



Reliability of the Impregnated Boron Compounds, Citric Acid- and Heat-Treated Samama (*Anthocephalus macrophyllus*) Wood against the Fungal and Termite Attacks

Trisna PRIADI¹ · Guruh Sukarno PUTRA¹ · Tekat Dwi CAHYONO^{2,†}

ABSTRACT

This research aimed to evaluate the durability of Samama (*Anthocephalus macrophyllus*) wood treated with boron preservatives, citric acid (CA), and heating against termites. Wood samples were impregnated firstly with 5% boron solutions, such as boric acid, borax and boric acid + borax combination at 1:1 (w/w). The second impregnation used 5% CA. The impregnations were conducted in a pressure tank at 7 kg/cm² for 4 hours. After impregnation, the samples were heat treated at 80°C or 160°C. All the treated and control samples were exposed to decay fungi, drywood termites and subterranean termites based on SNI 7207:2014 standard. The results showed that boron preservatives reduced fungal attacks on Samama wood. The combination treatment of boric acid, CA and heat treatment at 160°C was also effective to increase the resistance of Samama wood against white- and brown rot fungi, and drywood termites. Heat treatment consistently improved the resistance of Samama wood from decay fungi.

Keywords: boron, citric acid, durability, heat treatment, impregnation

1. INTRODUCTION

Boron compound is rarely applied alone in recent studies; rather it has been engineered by altering the method and adding other materials. The additional material can be used to cover wood surface (Priadi *et al.*, 2021; Temiz *et al.*, 2008) or as adhesive (Thévenon *et al.*, 1998; Verly Lopes *et al.*, 2020) to keep boron consistency in the wood.

Wood modification is potential to improve low dura-

bility wood, particularly from fast growing species, such as Samama (*Anthocephalus macrophyllus* (Roxb.) Havil) (Cahyono *et al.*, 2015). Samama wood belongs to strong class II-III and durability class IV (Halawane, 2015; Tuheteru *et al.*, 2019). This means that Samama wood has low durability and needs protection or preservation against biodeterioration agents. Combination treatment of boron, methyl methacrylate (MMA) and heating effectively increased dimensional stability, flexural strength and durability of Samama wood (Cahyono *et al.*, 2020;

Date Received September 26, 2022, Date Revised October 17, 2022, Date Accepted December 14, 2022

¹ Forest Product Department, Faculty of Forestry and Environment, IPB University, Bogor 16680, Indonesia

² Forest Products Department, Universitas Darussalam Ambon, Ambon 97128, Indonesia

† Corresponding author: Tekat Dwi CAHYONO (e-mail: tekatdwicahyono@gmail.com, <https://orcid.org/0000-0002-3010-7656>)

© Copyright 2023 The Korean Society of Wood Science & Technology. This is an Open-Access article distributed under the terms of the Creative Commons Attribution Non-Commercial License (<http://creativecommons.org/licenses/by-nc/4.0/>) which permits unrestricted non-commercial use, distribution, and reproduction in any medium, provided the original work is properly cited.

Priadi *et al.*, 2020). In addition, the dimensional stability of Samama wood also increased after being treated with boron, castor bean oil and heating (Priadi *et al.*, 2021). Moreover, eco-friendly adhesive materials, such as citric acid (CA), could be applied to modify the fast-growing wood (Lee *et al.*, 2020).

Citric acid can be used in wood modification combined with other materials. CA can increase wood dimensional stability (Vukusic *et al.*, 2006) and compression strength (Šefc *et al.*, 2012). CA can not improve the performance of fir and beech woods against weathering (Miklečić and Jirouš-Rajković, 2011), but can protect *Melaleuca cajuputi* wood from termite attack (Tarasin and Rattanapun, 2019). CA can be combined with glycerol (Schorr *et al.*, 2018), glucose (He *et al.*, 2016) and sorbitol (Larnøy *et al.*, 2018). Beck (2020) suggested that wood polyesterified with sorbitol and CA has been proved to block the white rot and brown rot attack on *Pinus sylvestris* wood. In addition Salem *et al.* (2019) reported that the combination of *Acer saccharum* inner and outer bark extracts and CA manages to protect *Leucaena leucocephala* wood from mold attack.

The combination of CA and boron as a wood modifying material is still rarely used. Therefore, research is needed to determine the CA and boron's ability to repress the attack of wood-destroying organisms.

2. MATERIALS and METHODS

2.1. Material preparation

Samama (*Anthocephalus macrophyllus*) logs were obtained from a community forest in Bogor, West Java. The tree age was 9 years with the diameter of 42 ± 3 cm. The logs were turned into 15 cm thick boards and kiln-dried to 15% moisture content. The temperature used in based on the drying schedules, gradually from 50°C up to 80°C. The boards were cut into some sample sizes (Table 1). The replication for each treatment com-

Table 1. Durability test sample dimension of Samama wood

Test sample	Dimension (l × w × h, cm ³)
White rot decay test	5 × 2.5 × 1.5
Brown rot decay test	5 × 2.5 × 1.5
Drywood termite test	5 × 2.5 × 2
Subterranean termite test	2 × 2 × 0.5
Field test	37 × 2 × 2

bination was 5 for every testing.

2.2. Double impregnation process

The first stage of impregnation used boric acid (BA), borax (B), and a mixture of boric acid and borax (BA + B) at a 1:1 (w/w) ratio. These boron solutions were in 5% concentration. The impregnation was conducted at 7 kg/cm² pressure for 4 hours. After the first impregnation, the samples were dried in a heating oven at 40°C for 4 hours. The second impregnation used 5% citric acid for 4 hours at 7 kg/cm² pressure. Then the samples were oven dried at 40°C for 4 hours. The next process was heat treatment at 80°C or 160°C for 4 hours. Boron retention was calculated based on the ratio between the weight of impregnated boron and the sample volume. Meanwhile, the weight percent gain (WPG) was calculated based on the ratio of the weight of impregnated citric acid to the weight of the sample before impregnation. Prior to testing, the samples were conditioned at room temperature (28°C) for 2 weeks.

2.3. Decay test against white rot and brown rot fungi

The decay test used SNI 7207:2014 standard (SNI, 2014). Prior to the test, wood samples were dried in an oven at 80°C to a constant weight (W₁; about 7 days). Wood samples were tested against white rot (*Schizophy-*

llum commune) and brown rot (*Tyromyces palustris*) fungi in potato dextrose agar (PDA) media. The inoculation process was done aseptically in a laminar air flow. The incubation was carried out for 12 weeks at room temperature (28°C). Finally, the samples were cleaned from the attached mycelium then oven dried at 80°C to a constant weight (7 days) and weighed (W2). The weight loss (WL) was calculated using Equation (1).

$$WL = \frac{W1 - W2}{W1} \times 100 \quad (1)$$

2.4. Durability test against drywood termite

In the durability test against drywood termites, wood samples were oven dried at 80°C to a constant weight (W1). Then a PVC pipe with 1.5-inch diameter and 2.5 cm length was stuck on the wide surface of each wood sample using PVC glue. Furthermore, 50 workers of drywood termites (*Cryptotermes cynocephalus*) were placed into the pipe and covered with cotton. The test was carried out in a dark room for 12 weeks. After the test, the cleaned samples were oven dried at 80°C to a constant weight (W2). The weight loss was calculated using Equation (1).

2.5. Durability test against subterranean termite

All wood samples were oven dried at 80°C to a constant weight (W1). Then every sample was put in a glass jar, standing on the jar bottom and leaning to its wall. Furthermore, 200 g of moisturized sterile sand was added into the jar. The sand moisture content was 13% below its water holding capacity. The test against the subterranean termite began when 200 worker-caste of subterranean termites (*Coptotermes curvignathus*) were placed into the jar. All the jars were placed in a dark room for 4 weeks. Finally, all the samples were taken from the jar, cleaned from the sands and oven dried at

80°C to a constant weight (W2). The weight loss of the sample was calculated using Equation (1).

2.6. Field test of durability

All wood samples were oven dried at 80°C to a constant weight (W1) and placed in soil ground, so 26 cm of each sample length was underground surface. The distance between buried samples was 30 cm × 60 cm. This ground exposure test was conducted for 12 weeks. Finally, all the wood samples were removed from the ground, cleaned, and observed for any damage by termites, and oven dried at 80°C to a constant weight (W2). The wood damages were classified based on ASTM D 1758-02:2002 (ASTM International, 2002). In addition, the weight loss of the sample was also calculated using Equation (1).

2.7. Data analysis

The effect of treatment on each testing variable was analyzed using completely randomized factorial design with 3 factors. Factor A was preservation (without boron, boric acid, borax, boric acid-borax mixture). Factor B was citric acid treatment (citric acid, without citric acid). Factor C was heat treatment (80°C and 160°C; Table 2). The analysis of variance (ANOVA) was determined using Statistica ver. 10. When the ANOVA result was significant at 95% confidence interval, the Duncan test was conducted.

3. RESULTS and DISCUSSION

3.1. Retention and weight percentage gain

The first impregnation process of Samama wood resulted in the retention of borax (B) was higher than boric acid (BA) and mix boric acid-borax (BA + B). This could be related to the higher specific weight of borax than boric acid (BA; Fig. 1). Gecer *et al.* (2015)

Table 2. Test sample and treatment

Test sample type	Impregnation		Heat treatment (°C)	Repetition
	Stage I	Stage II		
A	WP	WCA	80	5
B	WP	WCA	160	5
C	WP	CA	80	5
D	WP	CA	160	5
E	BA	WCA	80	5
F	BA	WCA	160	5
G	BA	CA	80	5
I	BA	CA	160	5
J	B	WCA	80	5
K	B	WCA	160	5
L	B	CA	80	5
M	B	CA	160	5
N	BA + B	WCA	80	5
O	BA + B	WCA	160	5
P	BA + B	CA	80	5
Q	BA + B	CA	160	5

WP: without preservative, WCA: without citric acid, BA: boric acid, CA: citric acid, B: borax.

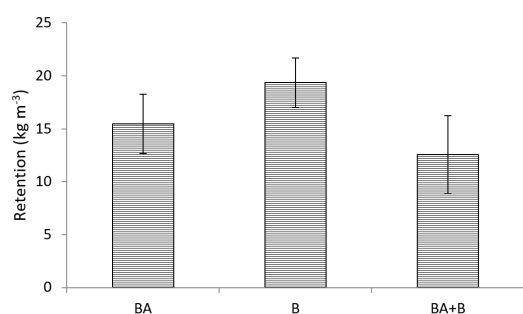


Fig. 1. Retention of boric acid (BA), borax (B), boric acid + borax (BA + B) in Samama wood.

also reported that the retention of borax was higher than that of BA and the mixture of both. The same phenomenon was also found in oak tree, where borax had 18% higher retention than BA (Perçin *et al.*, 2015).

The weight percent gain (WPG) of citric acid (CA) in heat-treated at 80°C was higher than that heat-treated at 160°C, which were 8%-10% and 1%-6%, respectively. The highest WPG was seen in the treatment of borax, CA and heat-treated at 80°C (Fig. 2). The higher temperature caused more water evaporation and some chemical changes in wood, particularly hemicelluloses and extractives. As reported by Doll *et al.* (2006) that during wood modification, water was released. In addition, Mubarok *et al.* (2020) reported that high temperature treatment under acid condition could degrade wood components.

3.2. Durability against brown- and white rot

This research revealed that CA impregnation could

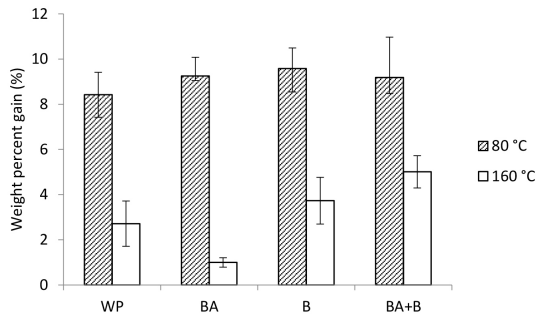


Fig. 2. Weight percent gain (WPG) of citric acid in Samama wood after boric acid (BA), borax (B), boric acid + borax (BA + B), without preservative (WP) treatments and heated at 80°C and 160°C.

not protect Samama wood from brown rot fungus *T. palustris*. Fig. 3 showed that citric acid treated sample had greater weight loss than sample without citric acid (WCA). Borax-citric acid treatment (BCA) also caused lower weight loss than borax-without citric acid treatment (BWCA), indicating that the protection from brown rot is more effective when CA is combined with borax. Furthermore, 160°C heating increased the durability of samama wood against brown rot.

Citric acid treatment did not improve wood resistance against white rot fungus *S. commune* (Fig. 4) that indicated by higher weight loss, except in citric acid

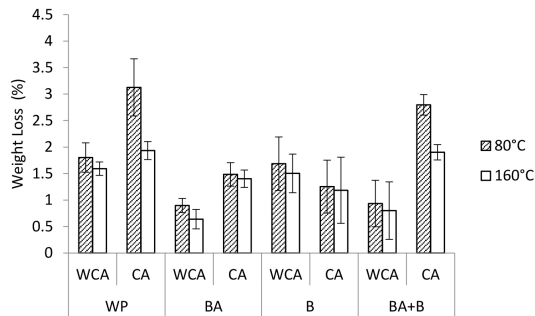


Fig. 3. Weight loss of treated Samama wood after brown rot decay test. WCA: without citric acid, CA: citric acid, WP: without preservative, BA: boric acid, B: borax.

followed by heat treatment at 160°C (WB-CA160) and borax-citric acid followed by heat treatment at 160°C (B-CA160). The best protection from brown- and white rot attack in Samama wood occurred in the treatment with BA followed by heat treatment at 160°C (BA-WCA160).

The heat treatment at 160°C consistently increased the durability of Samama wood. All samples treated in the temperature of 160°C had the weight loss lower than those with the heat treatment of 80°C. The variance analysis (ANOVA) showed that heat treatment, boron impregnation and citric acid modification have a significant effect on Samama wood’s durability against brown- and white rot attacks. All interactions between factors are statistically significant, except the interaction between CA and heat treatment ($p = 0.1558$) in white rot decay test. Previous research suggested that heat treatment degraded some chemical components of wood (Cao *et al.*, 2022; Esteves and Pereira, 2009; Schulz *et al.*, 2021). This degradation increased samama wood’s durability against fungal attacks.

3.3. Durability against drywood termites

Boron is one of the toxic chemical elements for drywood termites (DT). It is proven from the reduced DT

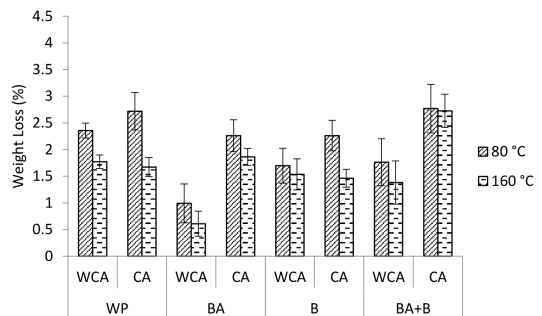


Fig. 4. Weight loss of treated Samama wood after white rot decay test. WCA: without citric acid, CA: citric acid, WP: without preservative, BA: boric acid, B: borax.

attack to the Samama wood impregnated with boron preservatives (B and BA; Fig. 5). Moreover, when boron preservative was combined with CA, the weight loss of wood was slightly less than that treated with boron preservative only. Heat treatment at 160°C inconsistently reduced drywood termite attack. The results of variance analysis also showed that the interaction of boron and citric acid had a significant effect on the weight loss of Samama wood by drywood termite attack. The previous research presented that the combination between boric acid and heat treatment at 140°C on Manii wood (*Mae-sopsis eminii*) decreased the DT (*C. cynocephalus*) attacks up to 50% (Istriana and Priadi, 2021). Furthermore, DT (*Incisitermes minor*) mortality was more than 80% in Sugi wood (*Cryptomeria japonica*) impregnated with disodium octaborate tetrahydrate (DOT; Kartal et al., 2020).

3.4. Durability against subterranean termites

Fig. 6 shows that BA plays an important role in maintaining Samama wood’s durability from subterranean termite attacks. The weight loss of the test sample treated with boric acid (BA-WCA) had the least weight loss than other treatments. This was in accordance with the

explanations made by Ahmed et al. (2004) stating that BA effectively reduced the weight loss of pine (*Pinus radiata*) and eucalyptus (*Eucalyptus regnans*) woods from the subterranean termite (*Coptotermes acinaciformis*) attacks. Boric acid was also reported successful to suppress the colonies of subterranean termites (*Heterotermes indicola* and *Odontotermes* sp.) which have low toxicity characteristics (Farid et al., 2015).

The combination of other treatments resulted in more weight loss than the untreated sample (WP-WCA). The second modification with CA failed to reduce the weight loss of wood by subterranean termites. In addition, the result of variance analysis also showed that the heat treatment at 160°C had no significant effect on subterranean termite attack.

3.5. Durability in field test

The weight loss of the control test sample (WP-WCA-80) after a 12-week ground contact field test was greater than 60% (Fig. 7), which was mainly attacked by subterranean termites. Samama wood’s weight loss tends to increase after being impregnated with CA. Heating at 160°C reduced the weight loss of boric acid and borax-treated samples (BA-WCA-160 and B-WCA-160), which were less than the control sample (WP-

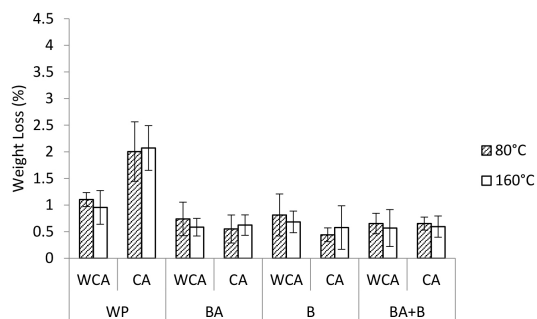


Fig. 5. Weight loss of treated Samama wood after drywood termite test. WCA: without citric acid, CA: citric acid, WP: without preservative, BA: boric acid, B: borax.

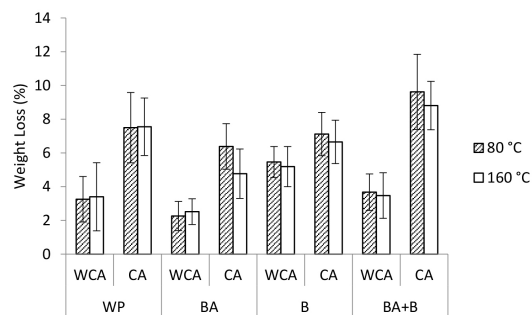


Fig. 6. Weight loss of treated Samama wood after subterranean termite test. WCA: without citric acid, CA: citric acid, WP: without preservative, BA: boric acid, B: borax.


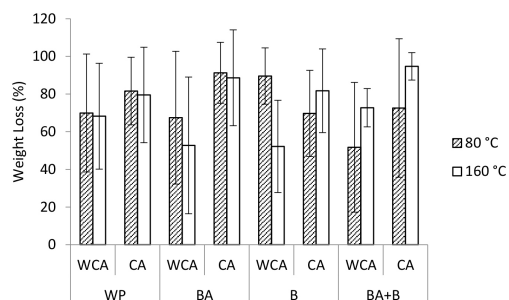


Fig. 7. Weight loss of treated Samama wood after field test. WCA: without citric acid, CA: citric acid, WP: without preservative, BA: boric acid, B: borax.

WCA-80) too. However, the boron impregnation and all interactions did not significantly affect the weight loss in this field test.

The visual evaluation of Samama wood after field test is presented in Fig. 8. The test sample damage indicated mainly due to subterranean termites. Most test samples have more than 75% damage, with their durability score being 0 based on ASTM D 1758-02:2002 standard. However, better resistance with the durability score 4 occurred in boric acid-heating 160°C and borax-heating 160°C treatments.

The test sample's weight loss and damage in the field test are influenced by many factors. The temperature and humidity in the test location increased the activity

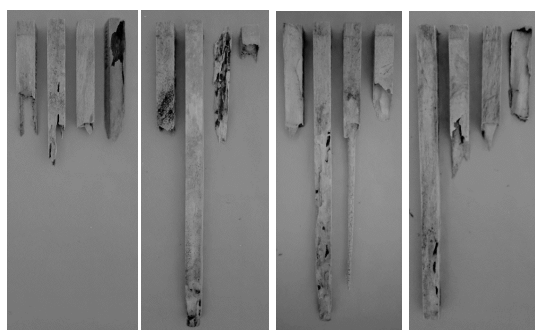

A B C D E F G H I J K L M N O P

Fig. 8. Damage to Samama wood after field test (letters indicate test sample types in Table 2).

of wood decay organisms, particularly termites (Arinana *et al.*, 2020). Boron is indeed not recommended for outdoor use due to its weak bond with the wood. In addition, CA was also reported to be washed at a certain amount during the test (Mubarok *et al.*, 2020; Rumbaremata *et al.*, 2019). The results of this research on the impregnation of boron combined with CA- and heat treatment in Samama wood confirm that boron and CA are effective for hampering wood-decay organism attack. In addition, they are not recommended for extreme conditions such as outdoor use, direct contact with the soil and high humidity.

4. CONCLUSIONS

The investigation on the reliability of boron, citric acid and heat treatment of samama wood against decay fungi and termites resulted in the following important points:

1. Boric acid impregnation increased Samama wood's durability against white- and brown rot fungi, and dry-wood- and subterranean termites.
2. The combination of boric acid or borax with citric acid and heating at 160°C reduced brown- and white rot decay.
3. Citric acid treatment could not protect Samama wood from wood-decay organism attack.
4. Heat treatment at 160°C resulted in a slight improvement in the resistance of Samama wood against brown- and white rot fungi and drywood termites.
5. The combination treatment of boron preservatives, citric acid and heating at 160°C was less effective when Samama wood was used for exterior uses and in direct contact with the soil.

CONFLICT of INTEREST

No potential conflict of interest relevant to this article was reported.

ACKNOWLEDGMENT

Not applicable.

REFERENCES

- Ahmed, B.M., French, J.R.J., Vinden, P. 2004. Evaluation of borate formulations as wood preservatives to control subterranean termites in Australia. *Holzforschung* 58(4): 446-454.
- Arinana, Hutapea, F.E., Nandika, D., Haneda, N.F. 2020. Field evaluation of subterranean termites palatability on treated pine wood in Alam Sinarsari Residence, West Java. *IOP Conference Series: Materials Science and Engineering* 935(1): 012012.
- ASTM International. 2002. Standard Test Method of Evaluating Wood Preservatives by Field Test with Stakes. ASTM D 1758-02. ASTM International, West Conshohocken, PA, USA.
- Beck, G. 2020. Leachability and decay resistance of wood polyesterified with sorbitol and citric acid. *Forests* 11(6): 650.
- Cahyono, T.D., Darmawan, W., Priadi, T., Iswanto, A.H. 2020. Flexural properties of heat-treatment Samama (*Anthocephalus macrophyllus*) wood impregnated by boron and methyl metacrylate. *Journal of the Korean Wood Science and Technology* 48(1): 76-85.
- Cahyono, T.D., Wahyudi, I., Priadi, T., Febrianto, F., Darmawan, W., Bahtiar, E.T., Ohorella, S., Novriyanti, E. 2015. The quality of 8 and 10 years old Samama wood (*Anthocephalus macrophyllus*). *Journal of the Indian Academy of Wood Science* 12(1): 22-28.
- Cao, S., Cheng, S., Cai, J. 2022. Research progress and prospects of wood high-temperature heat treatment technology. *BioResources* 17(2): 3702-3717.
- Doll, K.M., Shogren, R.L., Willett, J.L., Swift, G. 2006. Solvent-free polymerization of citric acid and D-sorbitol. *Journal of Polymer Science Part A: Polymer Chemistry* 44(14): 4259-4267.
- Esteves, B.M., Pereira, H.M. 2009. Wood modification by heat treatment: A review. *BioResources* 4(1): 370-404.
- Farid, A., Zaman, M., Saeed, M., Khan, M., Shah, T.B. 2015. Evaluation of boric acid as a slow-acting toxicant against subterranean termites (*Heterotermes* and *Odontotermes*). *Journal of Entomology and Zoology Studies* 3(1): 213-216.
- Gecer, M., Baysal, E., Toker, H., Turkoglu, T., Vargun, E., Yuksel, M. 2015. The effect of boron compounds impregnation on physical and mechanical properties of wood polymer composites. *Wood Research* 60(5): 723-738.
- Halawane, J.E., Hidayah, H.N., Kinho, J. 2015. Prospek Pengembangan Jabon Merah, *Anthocephalus macrophyllus* (Roxb.) Havil: Solusi Kebutuhan Kayu Masa Depan. Balai Penelitian Kehutanan Manado, Manado, Indonesia.
- He, X., Xiao, Z., Feng, X., Sui, S., Wang, Q., Xie, Y. 2016. Modification of poplar wood with glucose crosslinked with citric acid and 1,3-dimethylol-4,5-dihydroxy ethyleneurea. *Holzforschung* 70(1): 47-53.
- Istriana, N., Priadi, T. 2021. The resistance of modified Manii wood with boric acid and chitosan/glycerol and heating against fungi and termites. *IOP Conference Series: Earth and Environmental Science* 891: 012010.
- Kartal, S.N., Terzi, E., Yoshimura, T. 2020. Performance of fluoride and boron compounds against drywood and subterranean termites and decay and mold fungi. *Journal of Forestry Research* 31(4): 1425-1434.
- Larnøy, E., Karaca, A., Gobakken, L.R., Hill, C.A.S. 2018. Polyesterification of wood using sorbitol and citric acid under aqueous conditions. *International Wood Products Journal* 9(2): 66-73.
- Lee, S.H., Md Tahir, P., Lum, W.C., Tan, L.P., Bawon, P., Park, B.D., Osman Al Edrus, S.S., Abdullah,

- U.H. 2020. A review on citric acid as green modifying agent and binder for wood. *Polymers* 12(8): 1692.
- Miklečić, J., Jirouš-Rajković, V. 2011. Accelerated weathering of coated and uncoated beech wood modified with citric acid. *Drvna Industrija* 62(4): 277-282.
- Mubarok, M., Militz, H., Dumarçay, S., Gérardin, P. 2020. Beech wood modification based on *in situ* esterification with sorbitol and citric acid. *Wood Science and Technology* 54(3): 479-502.
- Perçin, O., Sofuoğlu, S.D., Uzun, O. 2015. Effects of boron impregnation and heat treatment on some mechanical properties of oak (*Quercus petraea* Liebl.) wood. *BioResources* 10(3): 3963-3978.
- Priadi, T., Lestari, M.D., Cahyono, T.D. 2021. Post-treatment effects of castor bean oil and heating in treated jabon wood on boron leaching, dimensional stability, and decay fungi inhibition. *Journal of the Korean Wood Science and Technology* 49(6): 602-615.
- Priadi, T., Orfian, G., Cahyono, T.D., Iswanto, A.H. 2020. Dimensional stability, color change, and durability of boron-MMA treated red jabon (*Antocephalus macrophyllus*) wood. *Journal of the Korean Wood Science and Technology* 48(3): 315-325.
- Rumbaremata, A., Cahyono, T.D., Darmawan, T., Kusumah, S.S., Akbar, F., Dwianto, W. 2019. Peningkatan kerapatan kayu Samama melalui pre-kompresi asam sitrat (Density improvement of Samama wood by pre-compression of citric acid). *Jurnal Ilmu dan Teknologi Kayu Tropis* 17(2): 122-133.
- Salem, M.Z.M., Mansour, M.M.A., Elansary, H.O. 2019. Evaluation of the effect of inner and outer bark extracts of sugar maple (*Acer saccharum* var. *saccharum*) in combination with citric acid against the growth of three common molds. *Journal of Wood Chemistry and Technology* 39(2): 136-147.
- Schorr, D., Blanchet, P., Essoua, G.G. 2018. Glycerol and citric acid treatment of lodgepole pine. *Journal of Wood Chemistry and Technology* 38(2): 123-136.
- Schulz, H.R., Acosta, A.P., Barbosa, K.T., Junior, M.A.P.S., Gallio, E., Delucis, R.Á., Gatto, D.A. 2021. Chemical, mechanical, thermal, and colorimetric features of the thermally treated eucalyptus grandis wood planted in Brazil. *Journal of the Korean Wood Science and Technology* 49(3): 226-233.
- Šefc, B., Trajković, J., Sinković, T., Hasan, M., Ištok, I. 2012. Compression strength of fir and beech wood modified by citric acid. *Drvna Industrija* 63(1): 45-50.
- Standar Nasional Indonesia [SNI]. 2014. Testing for Wood Resistance to Destructive Organisms. SNI 7207:2014. SNI, Jakarta Pusat, Indonesia.
- Tarasin, M., Rattanapun, W. 2019. Termite resistance of *Melaleuca cajuputi* wood treated with citric acid. *Agriculture and Natural Resources* 53(6): 662-666.
- Temiz, A., Alfredsen, G., Eikenes, M., Terziev, N. 2008. Decay resistance of wood treated with boric acid and tall oil derivatives. *Bioresource Technology* 99(7): 2102-2106.
- Thévenon, M.F., Pizzi, A., Haluk, J.P. 1998. Albumin borate: A new non-toxic, wide-spectrum, long-term wood preservative. In: Maastricht, Netherlands, Proceedings of IRG 29th Annual Meeting of the International Research Group on Wood Preservation.
- Tuheteru, F.D., Husna, Yusria, W.O. 2019. Jabon Merah. Deepublish, Yogyakarta, Indonesia.
- Verly Lopes, D.J., Barnes, H. M., dos Santos Bobadilha, G. 2020. Influence of heat treatment and tannin impregnation on boron depletion and wood durability. *Forests* 11(2): 201.
- Vukusic, S.B., Katovic, D., Schramm, C., Trajkovic, J., Šefc, B. 2006. Polycarboxylic acids as non-formaldehyde anti-swelling agents for wood. *Holzforschung* 60(4): 439-444.