



# The Application of Entomopathogenic Fungi *Metarhizium anisopliae*, *Beauveria bassiana*, and *Trichoderma harzianum* for *Coptotermes curvignathus* and *Cryptotermes cynocephalus* Termite Control in Indonesia

Niken SUBEKTI<sup>1,†</sup> · Ari SUSILOWATI<sup>2</sup> · Elizabeth Novi KUSUMANINGRUM<sup>3</sup> · Anita FADHILA<sup>1</sup> ·  
Sania SALSABILA<sup>1</sup> · Citra Anisah ZAHRA<sup>1</sup> · Nasiha Al SABRINA<sup>1</sup> · Ikhsan GUSWENRIVO<sup>4</sup> ·  
Yayan SANJAYA<sup>5</sup> · Cepi KURNIAWAN<sup>6</sup> · Apri Heri ISWANTO<sup>7</sup> · Mia MIRANTI<sup>8</sup>

## ABSTRACT

In Indonesia, *Coptotermes curvignathus* Holmgren and *Cryptotermes cynocephalus* Light termite attacks can damage wood and causing losses of 8.7 trillion rupiah per year. Wood treatment and soil barrier are very important to protect structures and their components from termite infestation. The application of synthetic chemicals that pose risks to the environment and human health. The growing movement to replace these chemicals with new termiticides that are safe for the environment in place of persistent organic pollutants. Efficacy performance in entomopathogenic fungi spores such as that produce decanoic acid, hexadecanoic acid, palmitic acid, and octadecadienoic acid are potential compounds that provide for ecofriendly termite control. Entomopathogenic fungal spores from *Metarhizium anisopliae*, *Trichoderma harzianum*, and *Beauveria bassiana*, as the active ingredient were formulated with nanocellulose was added as an inert ingredient to which helped to deliver the active ingredients on controlling the target pest, and enhance the utility ability of the product fungi to control termites. The mortality of these termites successively entomopathogenic fungi was the main cause of death. The higher concentrations being associated with of nanocellulose used affect increased the number of termites mortality. *M. anisopliae* paired with 60% nanocellulose concentrate was the best percentage for yielded the greatest *C. curvignathus* and *C. cynocephalus* termite control. In the field testing, *M. anisopliae* provided better, it showed the finest result of termite control rather than *B. bassiana* and *T. harzianum*. The results of the research indicate that entomopathogenic fungi can be used for Pest Control Management as the subterranean termite and drywood termite control.

**Keywords:** entomopathogenic, soil barrier, *Coptotermes curvignathus*, *Cryptotermes cynocephalus*

Date Received December 20, 2023; Date Revised January 16, 2024; Date Accepted March 26, 2024; Published May 25, 2024

<sup>1</sup> Biology Study Program, Faculty of Mathematics and Natural Sciences, Universitas Negeri Semarang, Semarang 50229, Indonesia

<sup>2</sup> Biology Study Program, Mathematics and Natural Sciences Faculty, Universitas Sebelas Maret, Surakarta 57126, Indonesia

<sup>3</sup> Biology Study Program, Faculty of Mathematic and Natural Sciences, Universitas Terbuka, Banten 15437, Indonesia

<sup>4</sup> Research Center for Applied Zoology, National Research and Innovations Agency (NRIA) the Republic of Indonesia, Jakarta Pusat 10340, Indonesia

<sup>5</sup> Biology Study Program, Faculty of Mathematic and Natural Sciences Education Faculty, Universitas Pendidikan Indonesia, Bandung 40154, Indonesia

<sup>6</sup> Chemistry Study Program, Faculty of Mathematic and Natural Sciences, Universitas Negeri Semarang, Semarang 50229, Indonesia

<sup>7</sup> Department of Forest Product, Faculty of Forestry, Universitas Sumatera Utara, Medan 20155, Indonesia

<sup>8</sup> Department of Biology, Faculty of Mathematics and Natural Sciences, Universitas Padjadjaran, Bandung 45363, Indonesia

† Corresponding author: Niken SUBEKTI (e-mail: [nikensubekti@mail.unnes.ac.id](mailto:nikensubekti@mail.unnes.ac.id), <https://orcid.org/0000-0003-1548-9219>)

© Copyright 2024 The Korean Society of Wood Science & Technology. This is an Open-Access article distributed under the terms of the Creative Commons Attribution Non-Commercial License (<http://creativecommons.org/licenses/by-nc/4.0/>) which permits unrestricted non-commercial use, distribution, and reproduction in any medium, provided the original work is properly cited.

## 1. INTRODUCTION

Termites are insects that damage wooden buildings as well as wood cellulose derivatives in furniture, clothes, papers, and other items (Arinana *et al.*, 2022; Lee *et al.*, 2019, 2020; Subekti *et al.*, 2018). The economic losses caused by termite attack in Indonesian housing reached IDR 8.7 trillion in 2015 (Arinana *et al.*, 2019). From an economic perspective, the most destructive termite species in Indonesia are subterranean termite *Coptotermes curvignathus* Holmgren and drywood termite *Cryptotermes cynocephalus* Light (Subekti and Fadhila, 2023).

Termiticides are often used to control termite attack. These chemicals include imidacloprid, alphacypermethrin, aldrin, dieldrin, endrin, heptachlor, and mirex. Those pesticides including of persistent organic pollutants (POPs) are organic chemical substances, that is, they are carbon-based. They possess a particular combination of physical and chemical properties such that, once released into the environment, they: remain intact for exceptionally long periods of time (many years); become widely distributed throughout the environment as a result of natural processes involving soil, water and, most notably, air; accumulate in the living organisms including humans, and are found at higher concentrations at higher levels in the food chain; and are toxic to both humans and wildlife.

In addition to harming non-target insects and increasing resistance to target insect pests, synthetic termiticides also present health concerns to humans (Pathak *et al.*, 2022). Water contamination, biodiversity loss, bioaccumulation, and biomagnification will all result from these chemical residues (Ayilara *et al.*, 2023). Using natural microorganisms, such as entomopathogenic fungi (EPF), for biocontrol purposes could prove to be the most efficient and environmentally sustainable way to control termites. Entomopathogenic fungal infection can occur through the digestive and respiratory systems, but especially through the outer surface layer (Altinok *et al.*,

2019). In particular, EPF can kill termites by attaching to their surface and producing enzymes and toxins that enable sprout tubes to mechanically and chemically penetrate the integument. In addition, active fungal spores can be transmitted within termite colonies through trophallaxis (mutual feeding). EPF that have the potential to control insects include *Metarhizium anisopliae*, *Beauveria bassiana*, and *Trichoderma harzianum*.

Hussain *et al.* (2023) reported that *M. anisopliae*, *B. bassiana*, and *T. harzianum* were able to control fall armyworm *Spodoptera frugiperda*, with *M. anisopliae* being the most effective and mitigating 78.5% of the larval population. In a study by Calleri *et al.* (2010), *M. anisopliae* induced a mortality level of 83% in infected *Incisitermes schwarzi* (a species of drywood termites). Furthermore, Anggrawati and Ramadhania (2016) found that a conidial suspension of *B. bassiana* in MEB media led to an infection rate of 44.4% in termites, and Zhang *et al.* (2021) showed that *Trichoderma* sp. can effectively inhibit growth and reproduction of termites. In the latter study, that the mechanism of inhibition involved antibiosis and parasitism.

Termite control can be made more effective by combining toxic substances with attractants such as methyl eugenol that naturally occur in cellulose. The attract-and-kill principle is effective against pest species that live in cryptic habitats and complex environments that are hard to reach using simple techniques. This principle also makes use of trophallaxis in termite colonies (Achmad *et al.*, 2021). Nanocellulose is useful as an inhibitor of termite growth activities and also as an antimicrobial. One benefit of nanocellulose is that the particles have a large surface-to-volume ratio, which makes attractants within the cellulose more detectable by termites. A liquid formulation containing nanocellulose and EPF could be used for termite control. The nanocellulose would serve as an attractant, while the EPF would work as a toxic substance to kill termites.

The innovation in the current study involves using

nanotechnology to modify cellulose and combining the resultant nanocellulose with the three entomopathogenic fungal species to control termites. Our aim in this study was to analyze how effectively the combination of nanocellulose and the fungi *M. anisopliae*, *B. bassiana*, and *T. harzianum* is able to control subterranean termites and drywood termites. Parameters observed included weight loss from termite wood consumption (preference test), termite mortality percentage, and termite behavior test (like-dislike test). In addition, we analyzed the organic compounds contained in the EPF.

## 2. MATERIALS and METHODS

### 2.1. Sample preparation

Two species of termites were used in this research. Subterranean termites and drywood termites were obtained from the colony collection in the Biology Laboratory of Universitas Negeri Semarang. The fungi for combination with nanocellulose, including *M. anisopliae*, *B. bassiana*, and *T. harzianum*, were obtained from the Integrated Laboratory for Bioproduct (iLab) National Research and Innovation Agency, Cibinong, West Java and the Microbiology Laboratory of Universitas Padjadjaran in West Java.

#### 2.1.1. Entomopathogenic fungi multiplication

Fungi were propagated on solid media. Thirty-nine grams of potato dextrose agar (PDA) oxid was mixed with 1 L of sterile distilled water. After homogeneity, the mixture was sterilized in an autoclave for 30 minutes at 121°C. Subsequently, 500 mg of chloramphenicol was added to the erlenmeyer flask, which was then sealed with aluminum foil and sterilized at 121°C for 15 minutes. Afterward, about 25 mL of media was poured into multiple petri dishes and allowed to solidify. Next, a cork borer was used to remove a plug of solid media from the plates containing fungal isolates, which was

then planted in new solid media. The petri dishes were covered, wrapped, and taped tightly and then left at 28°C (room temperature) for 14 days for the fungi to grow (Azzahra *et al.*, 2020).

#### 2.1.2. Spore density suspension production

The fungi that grew in the PDA were harvested and then suspended in 9 mL of sterile distilled water and vortexed for 1 minute to obtain the required spore density (dilution 10<sup>-7</sup>). Spore density was determined with a hemocytometer by dripping 0.2 mL on the calculation field and letting it stand for 1 minute. The number of conidia was calculated with × 400 magnification using the following formula:

$$S = R \times P \times V \quad (1)$$

Where *S* = spore density; *R* = average number of spores in five fields of view of the hemocytometer; *P* = dilution; and *V* = volume of the container (10<sup>4</sup>) mL (Shackleton *et al.*, 2015).

#### 2.1.3. Formulation

Liquid nanocellulose was produced by dissolving 20 g of microcrystalline cellulose in 2 L of distilled water, which was then put into a super grinder to create nanoparticles. Nanocellulose was used to make 20%, 40%, and 60% solutions by respectively mixing 20 mL, 40 mL, and 60 mL of the liquid nanocellulose in sterile distilled water up to 100 mL. After that, 60 mL of sodium tripolyphosphate solution (0.4%) was slowly added using a syringe. Next, 10 mL of EPF with area spore density was added, after which the sample was stirred at a speed of 300 rpm for 6 hours at room temperature. The solution was then incubated for 12 hours in the oven 45°C to destroy all microbes other than the fungi. The incubated sample was centrifuged at a speed of 2744 RCF for 20 minutes at 28°C. The supernatant was removed, while the pellet was cleansed

with distilled water, and kept at  $-20^{\circ}\text{C}$  for 2 days (Wu *et al.*, 2021). The control used in this research was a 40% nanocellulose formulation. The composition of the control was the same as the 40% nanocellulose test formulation, namely there was a nanocellulose solution, sodium tripolyphosphate solution (0.4%), and 10 mL of EPF.

## 2.2. Entomopathogenic fungi bioassay tests

### 2.2.1. Drywood termite mortality test

A mortality test (JIS, 2016) was used to determine the total number of drywood termites that died as a result of infection with EPF. Observations were carried out every day for 3 months.

Wood pieces that were  $2\text{ cm} \times 2\text{ cm} \times 2\text{ cm}$  in size were sprayed with 0.5 mL of a formulation and then dried and moved into a glass test container (Neves and Alves, 2000; Fig. 1). Thirty drywood termites were placed in each glass container, which was then covered with mesh screen and plastic wrap with holes, following Romano and Acda (2017).

The mortality test was conducted by calculating the total number of termites that died. Termites that were infected with EPF were removed so that the other termites were not contaminated by them. Observations were carried out every day for 3 months.

### 2.2.2. Subterranean termite mortality test

The mortality test (JIS, 2016) was carried out using cylindrical acrylic containers (8-cm diameter, 6-cm

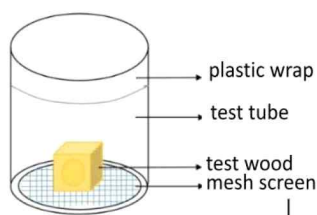


Fig. 1. The sketch of drywood termite test.

height; Fig. 2). The bottom of each container was covered with dental  $\pm 1\text{ cm}$  thick. Dental are made from alginate, a powder-shaped impression material which, when mixed with water which is used as a research site so that the temperature and humidity match the termite habitat. Wood samples were sprayed with 0.5 mL of a formulation and then dried and moved into glass test (Neves and Alves, 2000). For control, the treatment was done by spraying 0.5 mL of 40% nanocellulose formulation. Fifty termites, including 43 workers and seven soldiers, were added, and all treatments were incubated for 30 days in a dark room (JIS, 2010). Observations were carried out every day for 30 days. The time of death was determined by how many days passed until death occurred (Indrayani and Fatmawati, 2019).

### 2.2.3. Field testing of subterranean termite

The field test of subterranean termites was based on a capture-mark-recapture method. At each station point (i.e., test site), a PVC pipe (10-cm diameter, 20-cm length) was placed at a depth of 25 cm in the ground in the vicinity of subterranean termite tunnels. All test woods were oven-dried at  $60^{\circ}\text{C}$  and weighed with an analytical balance before being inserted into a bait tool in a predetermined area. After 7 days, each station was observed for termite activity. The termites were fed with 1-mm-diameter Whatman paper that was sprayed with methylene red. The red color of termites was used to determine whether the termites had consumed the bait or not. Next, termites were counted and returned to the station based on the sampling. This method was re-

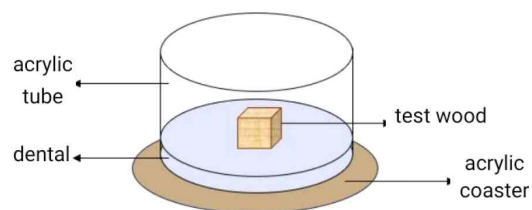


Fig. 2. Preference test of subterranean termites.

peated three times in the same colony (Su *et al.*, 1991). Observation of termite mortality was done every 7 days, and the number of all dead termites in the bait tool was recorded. The amount of bait consumption in the sample test was calculated after the mortality reached 100%. The observations were conducted until termite mortality reached 100%.

#### 2.2.4. Behavioral test (like-dislike test)

A bioassay (JIS, 2016) to determine termites' behavioral response to the formulation was conducted in a petri dish (Fig. 3). Afterwards, the container was put in the tray containing distilled water. Wood samples that had been weighed were sprayed with 0.1 mL of the liquid nanocellulose formulation or the control solution and then placed in the petri dish. Inside the petri dish included two testing woods, which are control group (A) and another wood used nanocellulose formulations and entomopathogenic fungi (*M. anisopliae*, *B. bassiana*, and *T. harzianum*) respectively (B). Ten drywood termites OR subterranean termite were placed in the petri dish with the two wood samples. The observation in the petri dish was held every 10 minutes for 300 minutes to observe termites' behavior (Oramahi and Yoshimura, 2013).

### 2.3. Analysis of entomopathogenic fungi using gas chromatography-mass spectrometry

The analysis of organic material in EPF was carried out using gas chromatography-mass spectrometry (GC-MS) Shimadzu GC-2010 Plus series with a column tem-

perature setting of 60°C held for 5 minutes, which was then raised 10°C per minute until it reached 250°C and held for 15 minutes. The injection temperature was 250°C, splitless injection mode. The MS ion source was set at 200°C and the interface was 250°C. The quantity of sample injected was 0.1 µL.

### 2.4. Data analysis

The preference test was calculated using a formula based on JIS (2010).

$$\text{Sample weight loss (\%)} = \frac{(W_1 - W_2)}{W_1} \times 100 \quad (2)$$

Where  $W_1$  = oven-dried sample before testing and  $W_2$  = oven-dried sample after testing.

The percentage of termite mortality was calculated using JIS (2010):

$$\text{Mortality (\%)} = \frac{N_1}{N_2} \times 100 \quad (3)$$

Where  $N_1$  = number of dead termites and  $N_2$  = total number of termites.

The percentage of mortality at each on-site observation was calculated using the formula of Kutana *et al.* (2018):

$$E (\%) = \frac{P_1 - P_2}{P_1} \times 100 \quad (4)$$

Where  $P_1$  = number of dead termites in all observa-

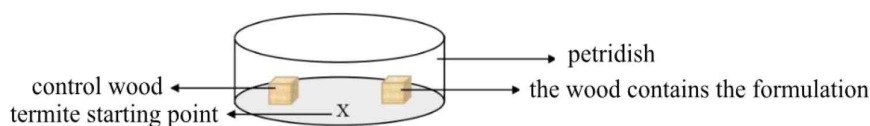


Fig. 3. The sketch of behavior test (like-dislike test).

tions and  $P_2$  = number of dead termites in each observation.

Mortality tests and bait weight difference tests were statistically analyzed using one-way ANOVA to determine whether differences in the fungal species and the percentage of nanocellulose in the formulation had significant effects on mortality and termite preference levels. If an effect was found from the results of the analysis, it was further examined using the least significant difference (LSD) test. Behavioral tests (like-dislike) were statistically analyzed using *t*-tests.

### 3. RESULTS and DISCUSSION

#### 3.1. Termite mortality

The ANOVA results showed significant differences between treatments and the controls ( $p = 0.00 < 0.05$ ), thus the different nanocellulose formulations and entomopathogenic fungus had an effect on the mortality of drywood termites (Table 1). To investigate the differences between treatment groups of nanocellulose formulation and entomopathogenic fungus, further tests were

conducted using the post hoc LSD test.

In Table 1 shows that in the control group, termite mortality was relatively low because the termites in this group received no treatment and storage conditions were conducive to survival. Based on the European standard EN118, an experiment is considered successful if two out of three samples in the control group have a survival value of  $> 50\%$ . In this study, the control treatment group had low mortality and termite survival was  $> 50\%$ .

*M. anisopliae* was the most effective type of fungus to control drywood termites because *M. anisopliae* has high toxicity that results in high termite mortality. In contrast, *B. bassiana* and *T. harzianum* induced relatively low mortality compared with *M. anisopliae*; these fungi are commonly used to inhibit the growth of several fungi that cause diseases in plants, including *Rigidoporus lignosus*, *Fusarium oxysporum*, *Rhizoctonia solani*, and *Sclerotium rolfsii*.

The EPF treatments with 60% nanocellulose were more effective because they induced 100% mortality in the fastest time, namely for 54 days. The results show that the higher the concentration of nanocellulose used, the higher the mortality rate of the termites. This out-

**Table 1.** The average mortality of drywood termites according to treatment

Group	Treatment	% Termite mortality (mean $\pm$ SD)
A0	Nanocellulose (control)	0.80 <sup>a</sup> $\pm$ 0.35
A1	Nanocellulose 20% and <i>Metarhizium anisopliae</i>	49.55 <sup>b</sup> $\pm$ 1.45
A2	Nanocellulose 40% and <i>M. anisopliae</i>	57.45 <sup>c</sup> $\pm$ 1.44
A3	Nanocellulose 60% and <i>M. anisopliae</i>	66.45 <sup>d</sup> $\pm$ 1.14
B1	Nanocellulose 20% and <i>Beauveria bassiana</i>	37.01 <sup>c</sup> $\pm$ 1.91
B2	Nanocellulose 40% and <i>B. bassiana</i>	53.03 <sup>d</sup> $\pm$ 1.04
B3	Nanocellulose 60% and <i>B. bassiana</i>	67.86 <sup>e</sup> $\pm$ 1.79
C1	Nanocellulose 20% and <i>Trichoderma harzianum</i>	69.09 $\pm$ 1.19
C2	Nanocellulose 40% and <i>T. harzianum</i>	79.37 $\pm$ 1.30
C3	Nanocellulose 60% and <i>T. harzianum</i>	97.43 $\pm$ 1.71

<sup>a-c</sup> Different letters indicate a significant difference between treatments.

come may have been due to termites not being able to easily recognize the volatiles released by fungi when nanocellulose concentrations were high, resulting in higher termite mortality (Hussain *et al.*, 2010). This finding is supported by Popat *et al.* (2012), who reported that the use of nano-sized cellulose in pesticide formulations applied to insects can produce a vast area of infection (Table 2).

The biocontrol formulations showed similar results in both termite species. The higher termite mortality rate associated with the higher nanocellulose concentrations may be attributable to the high surface area containing fungal conidia. This will further increase the pathogenicity of the formulation despite termites being able to detect the presence of EPF. Baiting techniques by using fungi as the active ingredient have been widely used, both for soil insects and other household insect pests (Skinner *et al.*, 2014). Sealing tunnel is often done to avoid the infection process of EPF (Staples and Milner, 2000).

The *B. bassiana* fungus works slowly and has a lower repellency level compared with the *M. anisopliae* strain. The *T. harzianum* fungus has no effectiveness

under *M. anisopliae* and *B. bassiana* because *T. harzianum* fungus contains harzianum acid compounds. This compound has less effect on subterranean termites.

In the subterranean termite field test, termite activity was high at low concentrations (Nanocellulose 20%), and there was low variability in termite responses and delayed toxicity. However, field tests with *B. bassiana* showed better results than those with *M. anisopliae* and *T. harzianum* in reaching 100% mortality. This outcome could be due to termites exposed to *B. bassiana* fungus having a slower response that allowed them to survive longer and consequently spread the fungus more widely through trophallaxis.

Table 3 shows that the treatment with 60% nanocellulose formulation and *M. anisopliae* had an average mortality of 100% at the sixth week. In the field test, 100% mortality rate was reached on the 49th day. A long time was required to produce biological effects that could reduce food consumption level of termites and reach 100% mortality. EPF can reproduce and sustain virulence when growing in their habitat (Singh *et al.*, 2011).

The attract-and-kill principle is effective against pest

**Table 2.** The average mortality of subterranean termites according to treatment

Groups	Treatment	% Termite mortality (Mean ± SD)
A0	Nanocellulose (control)	0.75 <sup>d</sup> ± 0.37
A1	Nanocellulose 20% and <i>Metarhizium anisopliae</i>	59.57 <sup>e</sup> ± 1.01
A2	Nanocellulose 40% and <i>M. anisopliae</i>	66.49 <sup>b</sup> ± 1.89
A3	Nanocellulose 60% and <i>M. anisopliae</i>	72.85 <sup>d</sup> ± 1.78
B1	Nanocellulose 20% and <i>Beauveria bassiana</i>	56.83 <sup>e</sup> ± 1.50
B2	Nanocellulose 40% and <i>B. bassiana</i>	66.94 <sup>f</sup> ± 2.10
B3	Nanocellulose 60% and <i>B. bassiana</i>	77.39 <sup>g</sup> ± 1.80
C1	Nanocellulose 20% and <i>Trichoderma harzianum</i>	57.05 <sup>h</sup> ± 1.45
C2	Nanocellulose 40% and <i>T. harzianum</i>	60.30 <sup>i</sup> ± 1.43
C3	Nanocellulose 60% and <i>T. harzianum</i>	65.85 <sup>j</sup> ± 1.31

<sup>b-j</sup> Different letters indicate a significant difference between treatments.

**Table 3.** The average mortality of subterranean termites in field tests according to treatment

Groups	Treatment	% Termite mortality (mean $\pm$ SD)
A0	Nanocellulose (control)	00.00 <sup>d</sup> $\pm$ 0.00
A1	Nanocellulose 20% and <i>Metarhizium anisopliae</i>	59.83 <sup>c</sup> $\pm$ 1.84
A2	Nanocellulose 40% and <i>M. anisopliae</i>	68.83 <sup>b</sup> $\pm$ 1.17
A3	Nanocellulose 60% and <i>M. anisopliae</i>	75.34 <sup>a</sup> $\pm$ 1.25
B1	Nanocellulose 20% and <i>Beauveria bassiana</i>	50.99 <sup>c</sup> $\pm$ 0.24
B2	Nanocellulose 40% and <i>B. bassiana</i>	56.90 <sup>d</sup> $\pm$ 0.35
B3	Nanocellulose 60% and <i>B. bassiana</i>	70.71 <sup>c</sup> $\pm$ 0.29
C1	Nanocellulose 20% and <i>Trichoderma harzianum</i>	59.66 <sup>f</sup> $\pm$ 1.61
C2	Nanocellulose 40% and <i>T. harzianum</i>	58.67 <sup>e</sup> $\pm$ 1.05
C3	Nanocellulose 60% and <i>T. harzianum</i>	60.67 <sup>h</sup> $\pm$ 1.21

<sup>a-h</sup> Different letters indicate a significant difference between treatments.

species with cryptic habitats and in complex environments that are usually inaccessible with typical application techniques. This principle utilizes the trophallaxis (mutual feeding) nature of termites in a colony (Achmad *et al.*, 2021). Foraging termites will eat the bait and then spread the toxic active ingredient within the colony. Biocontrol formulations made with entomopathogenic fungus mixed with nano-sized cellulose is expected to be a powerful combination in termite control. The use of nano-sized cellulose functions to expand the active surface area of the biocontrol formulation, which can increase the pathogenicity of the active ingredients of the EPF (Popat *et al.*, 2012).

### 3.2. Wood weight loss

The ANOVA results showed significant differences in the weight of wood samples treated with various formulations of entomopathogenic fungus and nanocellulose at  $p = 0.00 < 0.05$ . Thus, wood consumption by termites differed according to the specific formulations. To determine the differences between treatment groups, further tests were conducted using the post hoc LSD test. Data

on the average weight loss of test wood were generated from the post hoc LSD test results.

Table 4 shows that the formulations with 60% nanocellulose and entomopathogenic fungus resulted in lower rates of termite food consumption and required a shorter time to produce biological effects on drywood termites. Termites consumed the test wood treated with entomopathogenic fungal spores because it contained nanocellulose as an attractant compound. However, the decrease in termite food consumption eventually led to death due to the inhibition of organelles and abnormalities in termites' stomach function (Tables 5 and 6).

The *T. harzianum* fungus was associated with the least wood weight loss because termites continued to eat wood containing nanocellulose and *T. harzianum* has harzianum acid compounds that are slow acting. Harzianum acid has lower toxic properties compared with *B. bassiana* and *M. anisopliae*.

### 3.3. Behavioral (like-dislike test)

The results of the paired sample test in Table 7 show that the significance value in the like-dislike test of en-



**Table 4.** Weight loss of treated wood exposed to drywood termites

Groups	Treatment	Weight loss (g)
A0	Nanocellulose (control)	3.18 <sup>a</sup> ± 0.50
A1	Nanocellulose 20% and <i>Metarhizium anisopliae</i>	2.58 <sup>b</sup> ± 0.43
A2	Nanocellulose 40% and <i>M. anisopliae</i>	1.89 <sup>c</sup> ± 0.29
A3	Nanocellulose 60% and <i>M. anisopliae</i>	1.14 <sup>d</sup> ± 0.41
B1	Nanocellulose 20% and <i>Beauveria bassiana</i>	2.39 <sup>c</sup> ± 0.20
B2	Nanocellulose 40% and <i>B. bassiana</i>	2.10 <sup>d</sup> ± 0.13
B3	Nanocellulose 60% and <i>B. bassiana</i>	1.72 <sup>c</sup> ± 0.18
C1	Nanocellulose 20% and <i>Trichoderma harzianum</i> .	3.10 <sup>h</sup> ± 0.43
C2	Nanocellulose 40% and <i>T. harzianum</i> .	2.20 <sup>i</sup> ± 0.33
C3	Nanocellulose 60% and <i>T. harzianum</i> .	1.88 <sup>j</sup> ± 0.20

<sup>a-j</sup> Different letter ranks indicate a significant difference between treatments.

**Table 5.** Weight loss of treated wood exposed to subterranean termites

Groups	Treatment	Weight loss (g)
A0	Nanocellulose (control)	2.528 <sup>a</sup> ± 0.21
A1	Nanocellulose 20% and <i>Metarhizium anisopliae</i>	1.510 <sup>b</sup> ± 0.15
A2	Nanocellulose 40% and <i>M. anisopliae</i>	1.060 <sup>c</sup> ± 0.24
A3	Nanocellulose 60% and <i>M. anisopliae</i>	0.708 <sup>d</sup> ± 0.12
B1	Nanocellulose 20% and <i>Beauveria bassiana</i>	1.48 <sup>c</sup> ± 0.16
B2	Nanocellulose 40% and <i>B. bassiana</i>	1.13 <sup>d</sup> ± 0.18
B3	Nanocellulose 60% and <i>B. bassiana</i>	0.91 <sup>c</sup> ± 0.18
C1	Nanocellulose 20% and <i>Trichoderma harzianum</i>	4.95 <sup>h</sup> ± 0.14
C2	Nanocellulose 40% and <i>T. harzianum</i>	5.74 <sup>i</sup> ± 0.14
C3	Nanocellulose 60% and <i>T. harzianum</i>	6.64 <sup>j</sup> ± 0.11

<sup>a-j</sup> Different letter ranks indicate a significant difference between treatments.

tomopathogenic fungus with nanocellulose had a degree of freedom value of 29; the significance value was  $p = 0.00 < 0.05$ . Thus, the hypothesis is accepted. The results of the like-dislike test on all treatments show that termites always chose the control group (nanocellulose only).

### 3.4. Active compounds in fungi

GC-MS results of ethylacetate extracts of all fungi showed that *M. anisopliae*, *B. bassiana*, and *T. harzianum* contained several secondary metabolites, with different contents of the main compounds between fungi. These

**Table 6.** Weight loss of treated wood due to subterranean termites in field tests

Groups	Treatment	Weight loss (g)
A0	Nanocellulose (control)	429.62 <sup>a</sup> ± 1.97
A1	Nanocellulose 20% and <i>Metarhizium anisopliae</i>	367.10 <sup>b</sup> ± 1.55
A2	Nanocellulose 40% and <i>M. anisopliae</i>	363.61 <sup>c</sup> ± 1.73
A3	Nanocellulose 60% and <i>M. anisopliae</i>	308.17 <sup>d</sup> ± 1.46
B1	Nanocellulose 20% and <i>Beauveria bassiana</i>	373.84 <sup>e</sup> ± 0.63
B2	Nanocellulose 40% and <i>B. bassiana</i>	347.72 <sup>f</sup> ± 1.74
B3	Nanocellulose 60% and <i>B. bassiana</i>	326.45 <sup>g</sup> ± 1.89
C1	Nanocellulose 20% and <i>Trichoderma harzianum</i>	435.14 <sup>h</sup> ± 1.16
C2	Nanocellulose 40% and <i>T. harzianum</i>	364.94 <sup>i</sup> ± 1.83
C3	Nanocellulose 60% and <i>T. harzianum</i>	318.71 <sup>j</sup> ± 1.72

<sup>a-j</sup> Different letter ranks indicate a significant difference between treatments.

**Table 7.** Average time (minutes) required to choose between control and formulation

Treatment	Group	Mean ± SD	Significance, degree of freedom
1	T0	8.16 ± 2.06	$p < 0.05$ , $df = 29$
	T1	1.83 ± 2.06	
2	T0	7.10 ± 2.17	$p < 0.05$ , $df = 29$
	T2	2.90 ± 2.17	
3	T0	6.33 ± 1.18	$p < 0.05$ , $df = 29$
	T3	3.66 ± 1.18	

compounds included palmitic acid, octadecenoic acid, 1,3 dipalmitin, oleic acid/(Z)-9-octodecanoid acid, capric acid (decanoic acid), and eugenol. As reported previously, these compounds have potential as insecticides. Palmitic acid is a fatty acid that has been found in various studies to have insecticidal properties. It has been reported to affect insects like aphids, grasshoppers, caterpillars, and leaf suckers (Aker *et al.*, 2023; Saravanan, 2022). Palmitic acid, as one the phytochemicals in plant extracts, has shown insecticidal activities and is found in significant quantities in certain extracts such as castor bean

n-hexane extract that have been suggested as potential insecticides (Al-Harbi *et al.*, 2021; Sotelo-Leyva *et al.*, 2022).

Oleic acid/(Z)-9-octadecenoic acid is another fatty acid that is known for its insecticidal properties. It has been found effective in the form of insecticidal soap, and it has been particularly noted for its effectiveness against various larval stages of mosquitoes such as *Aedes aegypti*, *Anopheles stephensi*, and *Culex quinquefasciatus* (Zhang *et al.*, 2021) The C18:X acids, especially oleic and linoleic acids, have been reported as being effective against insect pests (Dasenaki *et al.*, 2022; Nirouman *et al.*, 2016).

Capric acid has been used in botanical products for the control of mosquitoes to interrupt disease transmission and is known to cause mortality in mosquito populations (Maw and House, 2012). It has also been indicated as one of the safer options for insecticides that would not endanger nontarget species like fish (Hikal *et al.*, 2017; Zhang *et al.*, 2022).

Eugenol has demonstrated a wide range of biological activities, including its use as an insecticide. It is effective against a variety of pests such as termites, mosqui-

toes, beetles, wasps, hornets, and other insects. Eugenol acts by targeting the nervous system of insects and can be used as a contact insecticide, a fumigant, or a feeding deterrent agent. It has also shown properties that make it toxic and repellent to certain beetles and ticks, in addition to its fumigant properties (Fernandes *et al.*, 2020; Fulton *et al.*, 2014). These compounds, through different mechanisms, contribute to the overall insecticidal properties of the extract. The presence of these compounds in the extract suggests potential applications in pest control.

In addition to these compounds, there are several specific compounds found in each of the EPF, as shown in Table 8.

#### 4. CONCLUSIONS

EPF have a potential role in controlling subterranean termites and drywood termites. In the current study, the main cause of mortality among subterranean termites and drywood termites was exposure to EPF, including *M. anisopliae*, *T. harzianum*, and *B. bassiana*. In addition,

the higher the concentration of nanocellulose used in the formulation, the higher the termite mortality. The formulation with 60% nanocellulose and *M. anisopliae* provided was the best subterranean termite and drywood termite control. In the field testing, *M. anisopliae* was associated with greater termite control than *B. bassiana* and *T. harzianum*. The main components of the three EPF are palmitic acid, octadecenoic acid, 1,3 dipalmitoyl/oleic acid/(Z)-9-octadecanoic acid, capric acid (decanoic acid), and eugenol. The results of this research can be used for pest control management for subterranean termites and drywood termites.

#### CONFLICT of INTEREST

No potential conflict of interest relevant to this article was reported.

#### ACKNOWLEDGMENT

We express our gratitude to the funder, the Ministry of Education and Culture, Research Technology Direc-

**Table 8.** Active compounds from *Metarhizium anisopliae*, *Beauveria bassiana*, and *Trichoderma harzianum*

Variable	Content (tR)		
	<i>M. anisopliae</i>	<i>B. bassiana</i>	<i>T. harzianum</i>
Common compounds			
Palmitic acid	45.06% (24,881)	38.33% (24,878)	44.23% (24,874)
Octadecenoic acid	21.98% (27,464)	24.93% (27,280)	23.62% (27,459)
1,3 Dipalmitoyl	6.92% (24,638)	3.97% (24,634)	6.61% (24,632)
Oleic acid/(Z)-9-octadecanoic acid	5.07% (27,094)	4.54% (27,090)	5.78% (27,080)
Capric acid/decanoic acid	4.68% (19,605)	3.69% (19,603)	2.55% (19,605)
Eugenol	1.62% (18,580)	1.62% (18,580)	0.22% (18,642)
Specific compounds			
Bicyclo[10.1.0]tridecene	1.78% (27,714)		
Octadecanoate butyl ester		1.01% (23,123)	
3,11-Dimethylnonane			1.32% (27,821)

torate and Community Service through Research and Community Service, Indonesia Research Grant collaboration with the contract number of DPA023.17.2.690645/2023.10. REVISI 2.

## REFERENCES

- Achmad, D.I., Ivansyah, O., Mutaqin, Z. 2021. Application of termite bait with variation of methyleugenol, pineapple peel extract and bintaro liquid smoke. *International Journal of Environmental & Agriculture Research* 7(3): 58-62.
- Aker, O., Eser, F., Yildirim, C. 2023. The laboratory evaluation of insecticidal activities and phytochemical analysis of *Marrubium astracanicum* Jacq. subsp. *astracanicum* Jacq. against *Callosobruchus chinensis* (L.) and *Callosobruchus maculatus* (Fabricius 1775). *South African Journal of Botany* 160: 667-672.
- Al-Harbi, N.A., Al Attar, N.M., Hikal, D.M., Mohamed, S.E., Latef, A.A.H.A., Ibrahim, A.A., Abdein, M.A. 2021. Evaluation of insecticidal effects of plants essential oils extracted from basil, black seeds and lavender against *Sitophilus oryzae*. *Plants* 10(5): 829.
- Altinok, H.H., Altinok, M.A., Koca, A.S. 2019. Modes of action of entomopathogenic fungi. *Current Trends in Natural Sciences* 8(16): 117-124.
- Anggrawati, P.S., Ramadhania, Z.M. 2016. Kandungan senyawa kimia dan bioaktivitas dari jambu air (*Syzygium aqueum* Burn. f. Alston). *Farmaka* 14(2): 331-344.
- Arinana, A., Rahman, M.M., Silaban, R.E.G., Himmi, S.K., Nandika, D. 2022. Preference of subterranean termites among community timber species in Bogor, Indonesia. *Journal of the Korean Wood Science and Technology* 50(6): 458-474.
- Arinana, A., Rauf, D., Nandika, D., Harahap, I., Sumertajaya, I.M. 2019. Model prediksi risiko kelas serangan rayap tanah di Provinsi DKI Jakarta berbasis spesies, tanah, dan iklim. In: Bandung, Indonesia, Prosiding Seminar Nasional PEI Cabang Bandung, pp. 170-178.
- Ayilara, M.S., Adeleke, B.S., Akinola, S.A., Fayose, C.A., Adeyemi, U.T., Gbadegesin, L.A., Omole, R.K., Johnson, R.M., Uthman, Q.O., Babalola, O.O. 2023. Biopesticides as a promising alternative to synthetic pesticides: A case for microbial pesticides, phytopesticides, and nanobiopesticides. *Frontiers in Microbiology* 14: 1040901.
- Calleri, D.V.II., Rosengaus, R.B., Traniello, J.F.A. 2010. Disease resistance in the drywood termite, *Incisitermes schwarzi*: Does nesting ecology affect immunocompetence? *Journal of Insect Science* 10(1): 44.
- Dasenaki, I., Betsi, P.C., Raptopoulos, D., Konstantopoulou, M. 2022. Insecticidal effect of *Pistacia lentiscus* (Anacardiaceae) metabolites against *Lobesia botrana* (Lepidoptera: Tortricidae). *Agronomy* 12(4): 755.
- Fernandes, M.J.G., Pereira, R.B., Pereira, D.M., Fortes, A.G., Castanheira, E.M.S., Goncalves, M.S.T. 2020. New eugenol derivatives with enhanced insecticidal activity. *International Journal of Molecular Sciences* 21(23): 9257.
- Fulton, M.H., Key, P.B., DeLorenzo, M.E. 2014. Insecticide Toxicity in Fish. In: *Organic Chemical Toxicology of Fishes*, Ed. by Tierney, K.B., Farrell, A.P., and Brauner, C.J. Elsevier, Amsterdam, The Netherlands.
- Hikal, W.M., Baeshen, R.S., Said-Al Ahl, H.A.H. 2017. Botanical insecticide as simple extractives for pest control. *Cogent Biology* 3(1): 1404274.
- Hussain, P.R., Meena, R.S., Dar, M.A., Wani, A.M. 2010. Carboxymethyl cellulose coating and low-dose gamma irradiation improves storage quality and shelf life of pear (*Pyrus communis* L., Cv. Bartlett/William). *Journal of Food Science* 75(9): M586-M596.
- Hussain, S., Farooq, M., Aslam, M.N., Zada, N. 2023.

- Insecticidal potential of eco-friendly mycoinsecticides for the management of fall armyworm (*Spodoptera frugiperda*) under *in vitro* condition. Bulgarian Journal of Agricultural Science 29(1): 124-130.
- Indrayani, Y., Fatmawati, D. 2019. Effect of bait density on consumption rates and mortality of subterranean termite *Coptotermes curvignathus*. Berkala Penelitian Hayati Journal of Biological Researches 24(2): 90-94.
- Japanese Industrial Standards [JIS]. 2010. Test Methods for Determining the Effectiveness of Wood Preservatives and Their Performance Requirements. JIS K 1571. Japanese Industrial Standards, Tokyo, Japan.
- Japanese Industrial Standards [JIS]. 2016. Performance Improvement of Management Systems: Guidelines for Daily Management. JIS Q 9026. Japanese Industrial Standards, Tokyo, Japan.
- Kutana, A.N., Muin, M., Arif, A. 2018. Produksi umpan rayap dari limbah bahan organik dan efektivitasnya dalam pengendalian serangan *Coptotermes* sp. Perennial Journal 14(2): 66-70.
- Lee, D., Kim, Y.K., Kim, Y.S., Kim, T.J. 2019. *Elizabethkingia miricola* Bml10, a new symbiotic bacterium isolated from the hindgut of the termite *Reticulitermes speratus* Kmt001. Journal of the Korean Wood Science and Technology 47(6): 692-699.
- Lee, J.M., Kim, Y.H., Hong, J.Y., Lim, B., Park, J.H. 2020. Exploration of preservatives that inhibit wood feeding by inhibiting termite intestinal enzyme activity. Journal of the Korean Wood Science and Technology 48(3): 376-392.
- Maw, M.G., House, H.L. 2012. On capric acid and potassium capricate as mosquito larvicides in laboratory and field. The Canadian Entomologist 103(10): 1435-1440.
- Neves, P.M.O.J., Alves, S.B. 2000. Grooming capacity inhibition in *Cornitermes cumulans* (Kollar) (Isoptera: Termitidae) inoculated with entomopathogenic fungi and treated with imidacloprid. Anais da Sociedade Entomológica do Brasil 29(3): 537-545.
- Niroumand, M.C., Farzkenari, M.H., Razkenari E.K., Amin, G., Khanavi, M., Akbarzadeh, T., Shams-Ardekani, M.R.. 2016. An evidence-based review on medical plants used as insecticide and insect repellent in traditional Iranian medicine. Iranian Red Crescent Medical Journal 18(2): e22361.
- Oramahi, H.A., Yoshimura, T. 2013. Antifungal and antitermitic activities of wood vinegar from *Vitex pubescens* Vahl. Journal of Wood Science 59(4): 344-350.
- Pathak, V.M., Verma, V.K., Rawat, B.S., Kaur, B., Babu, N., Sharma, A., Dewali, S., Yadav, M, Kumari, R., Singh, S., Mohapatra, A., Pandey, V., Rana, N., Cunill, J.M. 2022. Current status of pesticide effects on environment, human health and it's eco-friendly management as bioremediation: A comprehensive review. Frontiers in Microbiology 13: 962619.
- Popat, A., Liu, J., Hu, Q., Kennedy, M., Peters, B., Lu, G.Q.M., Qiao, S.Z. 2012. Adsorption and release of biocides with mesoporous silica nanoparticles. Nanoscale 4(3): 970-975.
- Romano, A.D., Acda, M.N. 2017. Feeding preference of the drywood termite *Cryptotermes cinocephalus* (Kalotermitidae) against industrial tree plantation species in the Philippines. Journal of Asia-Pacific Entomology 20(4): 1161-1164.
- Saravanan, G. 2022. Plants and phytochemical activity as botanical pesticides for sustainable agricultural crop production in India-MiniReview. Journal of Agriculture and Food Research 9: 100345.
- Shackleton, R., Kenaley, S.C., Hentcke, P., Stern, D., Fleming, T. 2015. Algae to Energy: Using and Re-using a Hemocytometer to Count Algae Cells. Boyce Thomson Institute, Ithaca, NY, USA.
- Singh, B.K., Pandey, J.G., Gupta, R.P., Verghese, A. 2011. Efficacy of entomopathogenic fungi for the

- management of onion thrips, *Thrips tabaci* Lind. Pest Management in Horticultural Ecosystems 17(2): 92-98.
- Skinner, M., Parker, B.L., Kim, J.S. 2014. Role of Entomopathogenic Fungi in Integrated Pest Management. In: Integrated Pest Management: Current Concepts and Ecological Perspective, Ed. by Abrol, D.P. Elsevier, Amsterdam, The Netherlands.
- Sotelo-Leyva, C., Toledo-Hernández, E., Navarro-Tito, N., Aguilar-Marcelino, L., Hernández-Salinas, G., Salinas-Sánchez, D.O., Peña-Chora, G. 2022. Chemical composition and aphidicidal properties of castor-bean leaves against *Rhopalosiphum maidis* and *Sipha flava* (Hemiptera: Aphididae). Chilean Journal of Agricultural Research 83(2): 228-235.
- Staples, J.A., Milner, R.J. 2000. A laboratory evaluation of the repellency of *Metarhizium anisopliae* conidia to *Coptotermes lacteus* (Isoptera: Rhinotermitidae). Sociobiology 36(1): 133-148.
- Su, N.Y., Ban, P.M., Schreffrahn, R.H. 1991. Suppression of foraging populations of the formosan subterranean termite (Isoptera: Rhinotermitidae) by field applications of a slow-acting toxicant bait. Journal of Economic Entomology 84(5): 1525-1531.
- Subekti, N., Fadhila, A. 2023. Termite identification attacks on buildings. Biosaintifika 15(2): 255-261.
- Subekti, N., Widiyaningrum, P., Yoshimura, T., Fibriana, F. 2018. The strength and termite resistance characteristics of fiberboards produced from the renewable bamboo biomass. Wood Research 63(3): 409-418.
- Wu, J., Du, C., Zhang, J., Yang, B., Cuthbertson, A.G.S., Ali, S. 2021. Synthesis of *Metarhizium anisopliae*-chitosan nanoparticles and their pathogenicity against *Plutella xylostella* (Linnaeus). Microorganisms 10(1): 1.
- Zhang, S., Blore, K., Xue, R.D., Qualls, W.A., Cermak, S., Zhu, J.W. 2021. Larvicidal activity of natural repellents against the dengue vector, *Aedes aegypti*. Journal of the American Mosquito Control Association 36(4): 227-232.
- Zhang, X.C., Jiang, M., Zang, Y.N., Zhao, H.Z., Liu, C.X., Liu, B.R., Xue, H., Schal, C., Lu, X.M., Zhao, D.Q., Zhang, X.X., Zhang, F. 2022. *Metarhizium anisopliae* is a valuable grist for biocontrol in beta-cypermethrin-resistant *Blattella germanica* (L.). Pest Management Science 78(4): 1508-1518.